

# Texture of Ultrafine-Grained Austenitic Stainless Steels Produced by Martensite Treatment



**Mostafa Eskandari<sup>1,2\*</sup>**

<sup>1</sup>Department of Materials Science & Engineering, Shahid Chamran University of Ahvaz, Iran

<sup>2</sup>Steel Research Center, Shahid Chamran University of Ahvaz, Iran

\*Corresponding author: Mostafa Eskandari, Department of Materials Science & Engineering, Steel Research Center, Faculty of Engineering, Shahid Chamran University of Ahvaz, Ahvaz, Iran, Email: m.eskandari1362@gmail.com

Submission: 📅 March 23, 2018; Published: 📅 May 14, 2018


## Mini Review

Austenitic stainless steels, for instance 301, 304, 316L, 321 and 310 are widely used in marine structures and petrochemical industry [1]. Such steels are typically characterized by good ductility and excellent overall corrosion resistance. However, they possess relatively low yield strength (200 to 360MPa), which hinders their structural applications. In the past years martensite treatment

including 90 percent cold-rolling followed by annealing treatment in the intervals temperatures of 650 to 800 °C have been applied to produce nano/ultrafine grained steels to improve the yield stress of material without sacrificing ductility [1-4]. The details of formation of nano/ultrafine-grained steels have been discussed in our previous work [1-3]. Table 1 depicts the experimental procedure to fabricate ultrafine-grain steels briefly.

**Table 1:** Effects of different processing parameters on the formation of ultrafine-grained steels.

Processing Conditions	Steel	Grain Size	Structure	El. (%)	$\sigma_{YS}$ (MPa)	$\sigma_{UTS}$ (MPa)	Ref.
95% CR at -15 °C+ 850 °C/2min	301	70±30nm	95 % $\gamma$	50	1970	-	[2]
95% CR at -15 °C + 750 °C/5min 90% CR at -196 °C	316L	150±50nm	95 % $\gamma$	95	-	1270	[1]
90% CR at -196 °C+ 650 °C/10min	321	0.3±0.1 $\mu$ m	98 % $\gamma$	-	-	-	[3]
90% CR at -196 °C+ 750 °C/5min	310	0.26±0.1 $\mu$ m	98 % $\gamma$	-	-	-	-

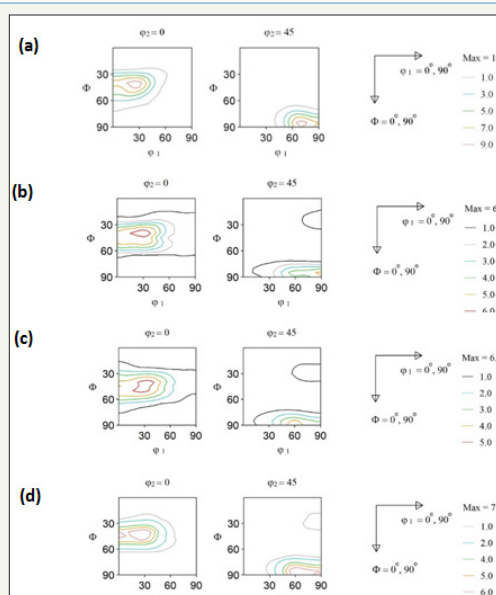

**Figure 1:** Orientation distribution function of austenite: (a) 316L steel, (b) 301 steel, (c) 321 steel, (d) 310 steel.

It is evident that preferred crystallographic orientation (texture) of ultrafine-grained steels affect the mechanical behavior of steels. It should be mentioned here that in present study the macro-texture measurements were carried out using a Bruker D8 advance diffractometer with Cr Ka radiation and a 2D Hi-star detector. The initial texture of as-received 301, 316L, 321, and 310 stainless steels was very weak (near random). Figure 1 display the orientation distribution function (ODF) sections  $0^\circ$ , and  $45^\circ$  of austenite phase of ultrafine-grained 316L, 301, 321, and 301 stainless steels. As is observed in the Brass  $\{110\}\langle 112\rangle$  and a Goss  $\{110\}\langle 100\rangle$  textures are appeared in ultrafine-grained steels.

### Conclusion

Two competitive phenomena influence the texture of ultrafine-grained steels; first, the remaining austenite phase (after cold-rolling) is recrystallized during annealing treatment; second, the strain-induced martensite is reverted to austenite during annealing. It is difficult to distinguish the contribution of mentioned effects on

texture evolution. However, by annealing at  $750^\circ\text{C}$  the contribution of martensite reversion to austenite is more pronounced on texture evolution compared to conventional recrystallization of remaining austenite [4].

### References

1. Eskandari M, Najafizadeh A, Kermanpur A (2009) Effect of strain-induced martensite on the formation of nanocrystalline 316L stainless steel after cold rolling and annealing. *Mater Sci Eng A* 519(1-2): 46-50.
2. Eskandari M, Kermanpur A, Najafizadeh A (2009) Formation of nanocrystalline structure in 301 stainless steel produced by martensite treatment. *Metall Mater Trans A* 40(9): 2241-2249.
3. Tihamiyu AA, Szpunar JA, Odeshi AG, Oguocha I, Eskandari M (2017) Development of ultra-fine-grained structure in AISI321 austenitic stainless steel. *Metall Mater Trans A* 48(12): 5990-6012.
4. Eskandari M, Mohtadi-Bonab MA, Basu R, Nezakat M, Kermanpur A, et al. (2015) Preferred crystallographic orientation development in nano/ ultrafine-grained 316L stainless steel during martensite to austenite reversion. *J Mater Eng Perform* 24: 644-653.



Creative Commons Attribution 4.0 International License

For possible submissions Click Here

Submit Article



### Research & Development in Material Science

#### Benefits of Publishing with us

- High-level peer review and editorial services
- Freely accessible online immediately upon publication
- Authors retain the copyright to their work
- Licensing it under a Creative Commons license
- Visibility through different online platforms