


Recent Advances and Future Prospects in Bionic Impregnated Diamond Bit

ISSN: 2643-7066

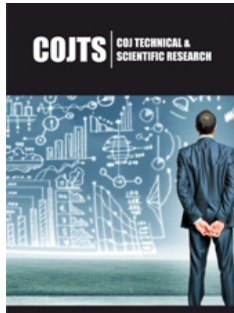

Dakang Fu, Liang Xu and Shaotao Xu*

State Key Laboratory of Deep Earth Exploration and Imaging, School of Engineering and Technology, China University of Geosciences, China

Abstract

Drilling in complex structure faces challenges like low efficiency and rapid wear. The bionic impregnated diamond bit presents an effective solution, developed through a closed-loop process of simulation-driven bionic design, advanced manufacturing and rigorous field validation. This review synthesizes recent advances of bionic impregnated diamond bit, demonstrating that it significantly outperforms conventional bits in challenging structures, achieving substantial improvements in both rate of penetration and service life. Future development should focus on broadening biological inspiration, advancing manufacturing and integrating real-time monitoring for intelligent drilling systems.

***Corresponding authors:** Shaotao Xu, State Key Laboratory of Deep Earth Exploration and Imaging, School of Engineering and Technology, China University of Geosciences, Beijing 100083, China

Submission: April 20, 2026

Published: May 19, 2026

Volume 6 - Issue 1

How to cite this article: Dakang Fu, Liang Xu and Shaotao Xu*. Recent Advances and Future Prospects in Bionic Impregnated Diamond Bit. COJ Tech Sci Res. 6(1). COJTS. 000629. 2026.
DOI: [10.31031/COJTS.2026.06.000629](https://doi.org/10.31031/COJTS.2026.06.000629)

Copyright@ Shaotao Xu, This article is distributed under the terms of the Creative Commons Attribution 4.0 International License, which permits unrestricted use and redistribution provided that the original author and source are credited.

Introduction

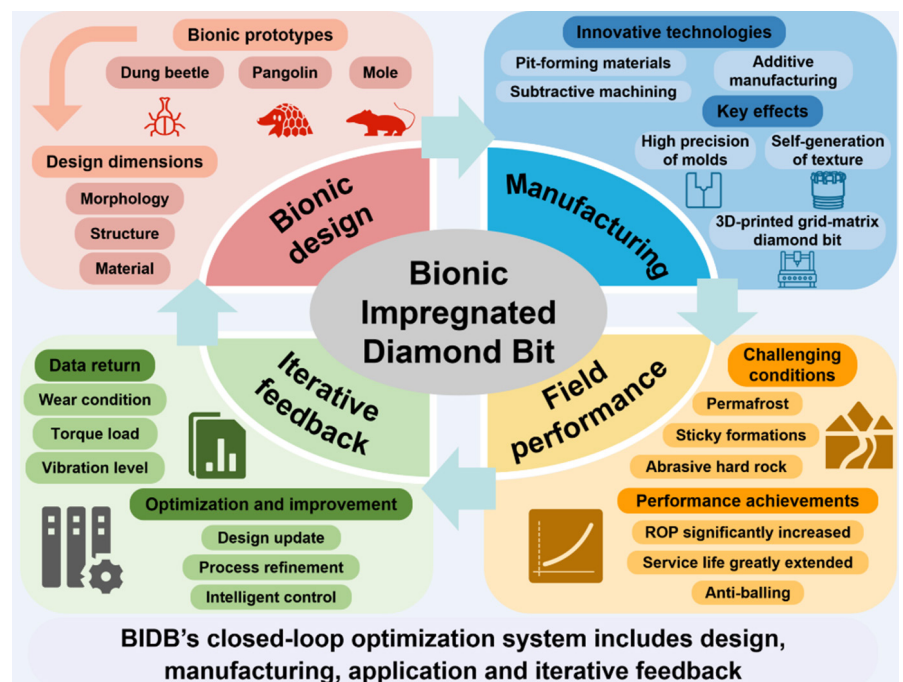


Figure 1: Closed-loop optimization system of BIDB.

The escalating demand for energy and resources makes their extraction ever more dependent on advances in drilling technology, which serves as an essential enabler in this domain. In recent years, drilling operations has been persistently challenged by complex conditions, including high temperatures, abrasive hard rocks and sticky structure [1]. As one of the core rock-breaking tools commonly used in drilling operations, the Impregnated Diamond Bit (IDB) plays a critical role. However, the IDB also exhibits drawbacks such as bit balling, a limited-service life and a low Rate of Penetration (ROP) [2]. Inspired by the

exceptional anti-adhesion, wear resistance and digging efficiency of animals like dung beetle, pangolin and mole, Bionic Impregnated Diamond Bit (BIDB) was pioneered by Prof. Sun Youhong's team as an effective solution to above drilling challenges [3]. The BIDB has so far undergone experimental validation [4], progressively developed into a mature product and found broad use [5]. This review systematically presents recent advances in the design, manufacturing and performance of BIDB, while also providing an outlook on future development directions (Figure 1).

Bionic Design Optimization Driven by Numerical Simulation

The design of BIDB primarily encompasses three aspects: Morphology, structure and material. From a morphological standpoint, the introduction of non-smooth surfaces inspired by animals is a key strategy based on bionic non-smooth theory to improve anti adhesion and wear resistance [6]. In terms of structure, macro-scale advances that resemble animal claws include integrated "one-body" reinforcement structures that greatly increase the overall strength of high-matrix bits [7] and stepped/heterogeneous cutters that boost rock-breaking efficiency [2]. Regarding material composition, examples include sea urchin teeth-inspired self-sharpening composites [2,8] and shell inspired surface texturing of PDC for reduced friction and thermal wear [9]. Furthermore, numerical simulation especially Finite Element Analysis (FEA) is crucial in the structural design of BIDB. For instance, the development of BIDB has incorporated FEA for optimizing bionic structures, such as the reverse rotary torque self-balancing dual drill bit and the annular-grooved bit [10,11]. This simulation-driven approach enables the transition from intuitive biomimicry to the rational design of coupled systems. Subsequently, field operational data inform its iterative optimization.

Advanced Manufacturing of Complex Bionic Architectures

The fabrication of BIDB requires advanced manufacturing processes to translate intricate bionic designs into functional tools. Beyond conventional hot-pressing sintering, early innovation involved embedding specially formulated "pit-forming" materials within the matrix. During drilling, the preferential wear of these materials enables the self-generation and maintenance of non-smooth surface textures [6]. For structurally complex bits, several key manufacturing techniques have been developed. To produce molds with intricate features such as stepped cutters, integrated reinforcement ribs and gradually opening waterways, three-dimensional subtractive machining of graphite is employed to ensure high precision [12]. Additive manufacturing has also been explored to enable the fabrication of complex bionic bits, including a 3D printed grid matrix diamond bit and a functionally gradient diamond composite [13,14]. Furthermore, a uniform temperature sintering process tailored for large and complex bits improves matrix homogeneity and reduces energy consumption by more than 50% [15]. Complementing these fabrication methods, the uniform arrangement of diamond grits within the matrix further enhances

bit stability and service life by ensuring consistent protrusion and even wear [16,17].

Field Application and performance Evaluation

The performance of BIDB has been rigorously validated through extensive field applications across diverse and challenging geological structures in China. Significant improvements in both service life and drilling efficiency have been consistently documented [18]. For instance, field tests conducted in drilling through granite at the Linglong gold mine in Shandong Province showed that BIDB increased ROP by 44% and extended service life by 74% compared to conventional bits [3,19]. In extremely cold and abrasive permafrost regions of Mohe, Heilongjiang Province, where the lithology is characterized by mudstone sandstone interbeds, bionic bits achieved a 22% higher ROP and a 73% longer service life compared to conventional bits [20]. Furthermore, the unique surface structures of BIDBs effectively mitigate bit-balling issues in soft, sticky structure by enhancing debris removal and maintaining cleaner cutting surfaces, a key factor in sustaining stable drilling parameters. These field results not only validate the potential of BIDB for challenging structures but also supply critical field data to guide iterative optimization.

Summary and Prospects

Above all, BIDB has established a mature, closed-loop development cycle of iterative optimization [1], encompassing bio-inspired design, advanced manufacturing and rigorous field validation [3,5,15]. Furthermore, BIDB has been successfully applied in extreme and complex geological settings, including hard rocks, permafrost regions and adhesive structure such as mudstone and shale, achieving significant performance improvements [19,20]. The future development of BIDBs should focus on three cutting-edge areas. First, inspiration should be drawn from a broader range of biological structures, such as claws, toes and carapaces, to develop innovative designs for new cutting teeth, integrated fluid channels and composite drill bit structures [21]. Second, advanced manufacturing technologies, particularly 3D printing and precision subtractive manufacturing processes [22], should be advanced to enable the low-cost, rapid and precise fabrication of complex BIDBs. Third, measurement technologies near the drill bit should be integrated into BIDBs to monitor real-time drilling parameters, thereby enabling adaptive control and further developing intelligent closed-loop drilling systems.

Acknowledgment

This work was supported by the Fundamental Research Funds for the Central Universities New Teacher Basic Scientific Research Ability Improvement, China (No.2652025021), Natural Science Foundation of Beijing, China (No.2252052), National Natural Science Foundation of China (U23A2025, U25B20122) and open foundation project of the Key Laboratory of Polar Geology and Marine Mineral Resources, Ministry of Education and Hainan Institute of China University of Geosciences, Beijing (HNPY-202510).

References

1. Gao K, Sun YH, Gao RF, Xu L, Wang CL, et al. (2009) Application and prospect of bionic non-smooth theory in drilling engineering. *Petroleum Exploration and Development* 36(4): 519-541.
2. Sun YH, Gao K, Zhang LJ, Li SS, Xu L, et al. (2012) High efficiency and wear resistance mechanism of coupled bionic impregnated diamond bits. *Journal of Jilin University* 42(S3): 220-225.
3. Gao K, Sun YH, Ren LQ, Cao PL, Li WT, et al. (2008) Design and analysis of ternary coupling bionic bits. *Journal of Bionic Engineering* 5(1): 53-59.
4. Gao K, Sun YH, Ren LQ, Wang WL, Xie XB, et al. (2009) Optimization design and experiment of non-smooth degree of bionic impregnated diamond bit. *Journal of Jilin University Engineering and Technology Edition* 39(3): 721-725.
5. Wang ZZ, Zhang ZZ, Sun YH, Gao K, Liang YH, et al. (2016) Wear behaviour of bionic impregnated diamond bits. *Tribology International* 94: 217-222.
6. Wang ZZ, Gao K, Sun YH, Zhang ZZ, Zhang SY, et al. (2016) Effects of bionic units in different scales on the wear behaviour of bionic impregnated diamond bits. *Journal of Bionic Engineering* 13(4): 659-668.
7. Gao K (2022) Research on bionic self-compensating integrated high-matrix impregnated diamond core bit. *Exploration Engineering Rock & Soil Drilling and Tunneling* 49(1): 16-24.
8. Killian CE, Metzler RA, Gong YT, Churchill TH, Olson IC, et al. (2011) Self-sharpening mechanism of the sea urchin tooth. *Advanced Functional Materials* 21(4): 682-690.
9. Yun JQ, Liu BC, Zhai LH, Qi B, Huang F (2025) Bionic surface texturing of polycrystalline diamond compact for enhanced tribological performance: A seashell-inspired strategy. *Journal of Materials Research and Technology* 38: 3039-3051.
10. Zhang C, Gao K, Zhao Y, Xie XB, Zhang CS, et al. (2023) Simulation and experimental study on rock-breaking mechanism of the reverse rotary torque self-balancing dual drill bit. *Arabian Journal for Science and Engineering* 48(12): 16571-16586.
11. Zhang C, Gao K, Lv XS, Liu ZH, Xie XB, et al. (2025) Experimental study on the rock-breaking mechanism of annular-grooved structure and rotary direction for impregnated diamond bits. *Geoenergy Science and Engineering* 249: 213812.
12. Zhang YX, Zhang ZB, Guo XC (2005) CAD/CAM technology for PDC bit mold processing based on Pro/E. *Petroleum Machinery* 34(5): 52-54.
13. Wu JJ, Zhang SH, Liu LL, Qu FL, Zhou H, et al. (2020) Rock breaking characteristics of a 3D printing grid-matrix impregnated diamond bit. *International Journal of Refractory Metals and Hard Materials* 89: 105212.
14. Kong XW, Wu JJ, Wu DY, Rong LR, Zhang SH (2024) Manufacturing and characterization of functionally gradient material from cemented carbide to diamond via filament-based material extrusion 3D printing. *Additive Manufacturing* 91: 104325.
15. Wang JL, Gao K, Li PS, Zhao Y (2023) Research on low-carbon, energy-saving sintering process with uniform temperature for drill bits. *Energies* 16(17): 6205.
16. Zhang DY (2017) Dispensing method enables orderly arrangement of diamonds and improves bit performance. *Diamond & Abrasives Engineering* 37(4): 11-14.
17. Sun YH, Wu HD, Li M, Meng QN, Gao K, et al. (2016) The effect of ZrO₂ nanoparticles on the microstructure and properties of sintered WC-bronze-based diamond composites. *Materials* 9(5): 343-350.
18. Wang CL, Sun YH, Liu BC, Wang YX (2011) Experiment and rock fragmentation mechanism analysis of bionic coupled impregnated diamond bit. *Journal of Central South University Science and Technology* 42(5): 1321-1325.
19. Xu L, Sun YH, Li ZW, Wang CL, Sun BL, et al. (2008) Experiment of bionic impregnated diamond bit in Shandong Linglong gold mine. *Geology and Exploration*: 79-82.
20. Cao Y, Liu BC, Ji SL, Li SS, Li XY (2012) Application of bionic impregnated diamond bit in gas hydrate exploration drilling in Mohe permafrost region. *Exploration Engineering Rock & Soil Drilling and Tunneling* 39: 77-81.
21. Zhao Y, Wen YM, Gao K, Wang JL, Zhang CS, et al. (2024) Study on rock-breaking mechanism and bit adaptive characteristics under the action of claw-toe impregnated diamond bit. *Geoenergy Science and Engineering* 236: 212752.
22. Wu JJ, Wang ZH, Zhang HT, Yang W, Zhang SH, et al. (2026) Additive manufacturing of diamond tools: A comprehensive review of technologies, materials, structures and challenges. *Diamond and Related Materials* 125: 113654.