

Fabrication of Rechargeable Lithium Ion Coin Cell using Triblock Polymer Electrolyte Poly (Vinylidene Chloride-Co-Acrylonitrile-Co-Methyl Methacrylate) with Lithium Perchlorate

Vengadesh Krishna M^{1,2}, Chitra R^{2,3} and Selvasekarapandian S^{2,4*}

¹Department of Chemistry, Government Arts College Coimbatore-641018, Tamil Nadu, India

²Materials Research Center, Coimbatore, Tamilnadu, India

³Department of Physics, Kongu Arts and Science College (Autonomous), Erode, Tamil Nadu, India

⁴Department of Physics, Bharathiar University, Coimbatore, Tamilnadu, India



*Corresponding author: Selvasekarapandian S, Department of Physics, Bharathiar University, Coimbatore, Tamilnadu, India

Submission:  September 26, 2020

Published:  November 17, 2020

Volume 1 - Issue 2

How to cite this article: Krishna MV, Chitra R, Selvasekarapandian S. Fabrication of Rechargeable Lithium Ion Coin Cell using Triblock Polymer Electrolyte Poly (Vinylidene Chloride-Co-Acrylonitrile-Co-Methyl Methacrylate) with Lithium Perchlorate. *Polymer Sci Peer Rev J.* 1(2). PSPRJ. 000509. 2020.

Copyright@ Selvasekarapandian S, This article is distributed under the terms of the Creative Commons Attribution 4.0 International License, which permits unrestricted use and redistribution provided that the original author and source are credited.

Abstract

Lithium ion conducting polymer electrolytes based on triblock polymer poly(vinylidene chloride-co-acrylonitrile-co-methyl methacrylate) (or) P(VdCl-co-AN-co-MMA)-LiClO₄ with tetrahydrofuran (THF) as solvent have been prepared by solution casting technique. Electrochemical impedance analysis of the polymer membranes reveals that the ionic conductivity of the polymer electrolyte increases with increase of LiClO₄ salt composition and the highest ionic conductivity of 1.9x10⁻³ S cm⁻¹ is observed for 40 wt% P(VdCl-co-AN-co-MMA)/60 wt% LiClO₄ at room temperature. A lithium ion coin cell has been fabricated with a configuration of Graphite||40m%P(VdCl-co-AN-co-MMA)/60 m% LiClO₄||LiFePO₄ and a maximum cell potential of 3.15V is observed which affirms applicability of membrane for solid state lithium ion batteries.

Keywords: Polymer; Lithium; Electrolytes; Discharging

Introduction

Battery electrolytes shuttle ions between the electrodes during charging and discharging process. Especially in lithium ion batteries, search of electrolyte remains a challenging aspect. Solid electrolytes in the place of liquid electrolytes hold promise for safety, long lasting and shape and design flexibility [1,2]. In this perspective, lithium ion conducting polymer electrolytes based on triblock polymer poly (vinylidene chloride-co-acrylonitrile-co-methyl methacrylate) (or) P(VdCl-co-AN-co-MMA) have been focused. The choice of host polymer P(VdCl-co-AN-co-MMA), here after mentioned as P(VdCL.) is owing to the presence of huge number of polar groups such as oxygen, nitrogen and chlorine [3]. It is a known fact that salt as ion provider significantly take part in determining the characteristic of polymer electrolytes such as conductivity, thermal and mechanical stability. In the present work, lithium perchlorate (LiClO₄) salt has been selected as ionic dopant due to this low molecular weight and low dissociation energy [4]. The present investigation aims to fabricate lithium ion full cell (CR 2032 coin cell) with highest conducting polymer membrane and explore the performance of the rechargeable lithium ion cell.

Experimental Method

Triblock copolymer P(VdCL.), LiClO₄ salt and tetrahydrofuran (THF) were purchased from Sigma-Aldrich. Appropriate amount of P(VdCL.) and LiClO₄ is dissolved in THF solvent at room temperature and stirred continuously. A homogeneous viscous liquid is obtained after continuous stirring for 4 days. The homogeneous liquid is transferred into petri dish and left undisturbed for evaporation. Finally, solid polymer electrolytes of composition 60 wt% P(VdCL.): 40 wt% LiClO₄, 50 wt% P(VdCL.): 50 wt% LiClO₄, 40 wt% P(VdCL.): 60 wt% LiClO₄ and 30 wt% P(VdCL.): 70 wt% LiClO₄ have been prepared by solution casting method.

Characterization

Prepared solid polymer electrolyte samples have been characterized by Electrochemical Impedance (EIS) analysis using HIOKI 3532-50 LCR HITESTER. The electrolyte samples have been sandwiched between two stainless-steel blocking electrodes over the frequency range of 42Hz to 5MHz.

Fabrication of CR2032 lithium ion coin cell

Cathode slurry has been prepared with a mixture of active material of lithium iron phosphate, acetylene black and PVDF

binder in the weight ratio of 8:1:1. N-methylpyrrolidone (NMP) has been used as a solvent. Cathode slurry has been coated over aluminium foil and cut into the disk of required size. Battery grade graphite powder has been coated over copper foil to fabricate anode electrode. A coin cell has been fabricated with a configuration of Graphite||40 wt% P(VdCl): 60 wt% LiClO₄||LiFePO₄. The charge-discharge cycles of fabricated coin cell has been analyzed by placing it in a battery holder. The photograph of the fabricated coin cell and the battery holder is shown in Figure 1.



Figure 1: Photograph of the fabricated coin cell and the battery holder.

Results and Discussion

EIS analysis

The ionic conductivity of the electrolytes has been determined using AC impedance technique at room temperature. A plot between the real and imaginary part of impedance as a function of frequency has been obtained and is complex impedance plot or Nyquist plot or cole-cole plot. Ionic conductivity studies for P(VdCl) with MgCl₂ has been reported by Ponraj et al and the ionic conductivity value for pure P(VdCl) is $3.07 \times 10^{-8} \text{Scm}^{-1}$ [3]. In the present investigation, ionic conductivity values of prepared polymer electrolytes have been obtained using

$$\sigma = \frac{l}{AR_b} \text{ Scm}^{-1}$$

Figure 2 shows the Nyquist plots of various compositions of polymer electrolytes. It is obvious that diminishing of semicircle is established with the increasing salt content. Almost, a spike is observed for the polymer composition of 40 wt% P(VdCl): 60 wt% LiClO₄ and the high ionic conductivity of $1.97 \times 10^{-3} \text{Scm}^{-1}$ is exhibited by this sample. (Table 1) provides the bulk resistance and ionic conductivity values of prepared electrolytes.

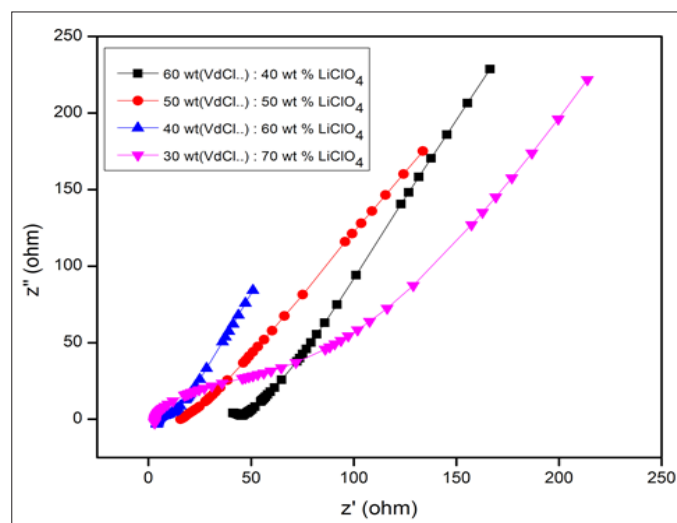


Figure 2: Nyquist plots of various compositions of polymer electrolytes.

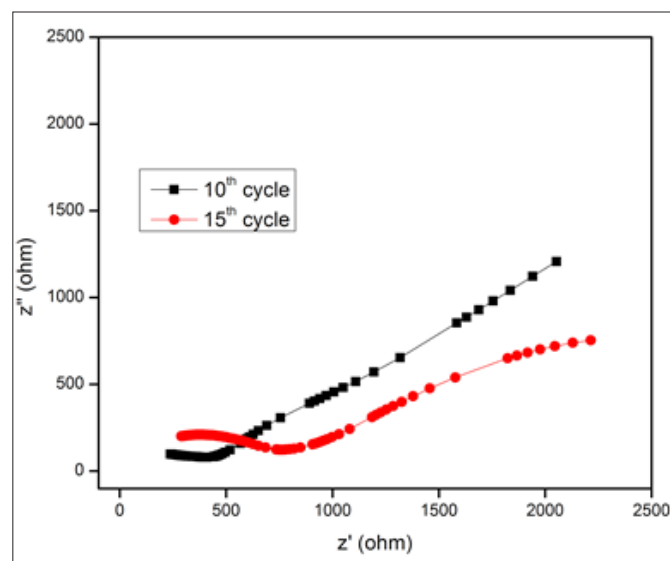
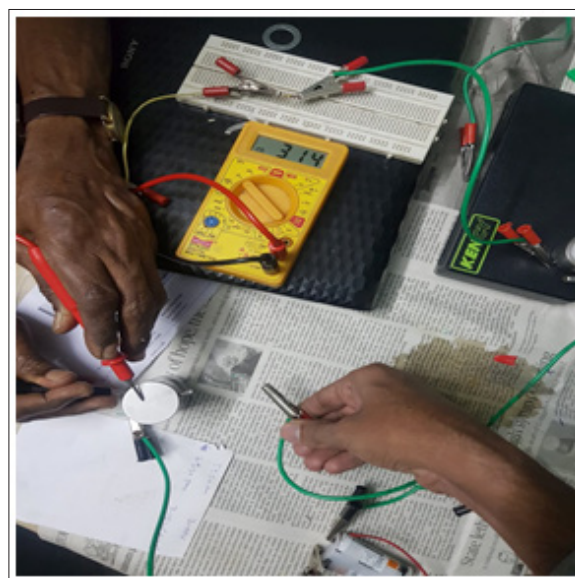
Table 1: Bulk Resistance & Ionic conductivity values of polymer electrolytes.

Polymer Composition	Bulk Resistance (ohm)	Ionic Conductivity Scm^{-1}
60 wt% P(VdCl): 40 wt% LiClO_4	48.25	3.43×10^{-4}
50 wt% P(VdCl): 50 wt% LiClO_4	15.66	7.10×10^{-4}
40 wt% P(VdCl): 60 wt% LiClO_4	6.65	1.97×10^{-3}
30 wt% P(VdCl): 70 wt% LiClO_4	85.42	4.37×10^{-5}

Charge-discharge characteristic of full cell

The fabricated cell is subjected to DC supply of 4V. Open circuit cell potential of 3.15V has been observed for the first cycle and then the cell has been charged for one hour. The discharge of the cell takes 4 hours to attain 0.6V. At the 15th cycle, the cell has been

charged to the maximum of 1.75V and the same discharge time is observed for this cycle too. The value of the cell resistance has been found to increase with charging cycles owing to interface resistance between electrodes and electrolyte of the cell. The Nyquist plot of fabricated coin cell at 10th and 15th cycle is shown in Figure 3 and the photograph of the fabricated cell potential is shown in Figure 4.

**Figure 3:** Nyquist plot of fabricated coin cell.**Figure 4:** Photograph of the fabricated cell potential.

Conclusion

The flexible solid polymer electrolytes of P(VdCl.): LiClO₄ have been prepared by the solution casting technique and the better ionic conductivity of the order of 10⁻³Scm⁻¹ is obtained by the composition 40 wt% P(VdCl.): 60 wt% LiClO₄. A fabricated full cell displayed a good charging –discharging cycles and proves the applicability of the membrane in lithium ion battery.

References

1. Pandey M, Joshi GM, Ghosh NN (2016) Ionic conductivity and diffusion coefficient of barium-chloride-based polymer electrolyte with poly(vinyl alcohol)-poly(4-styrenesulphonic acid) polymer complex. Bull Mater Sci 40(4): 655-666.
2. Meyer WH (1998) Polymer electrolytes for lithium-ion batteries. Adv Mater 10(6): 439-448.
3. Ponraj T, Ramalingam A, Selvasekarapandian S, Srikumar SR, Manjuladevi R (2019) Plasticized solid polymer electrolyte based on triblock copolymer poly(vinylidene chloride co acrylonitrile co methyl methacrylate) for magnesium ion batteries. Polymer Bulletin.
4. Perumal P, Selvasekarapandian S, Abhilash KP, Sivaraj P, Hemalatha R, et al. (2018) Impact of lithium chlorate salts on structural and electrical properties of natural polymer electrolytes for all solid state lithium polymer batteries. Vacuum 159: 277-281.

For possible submissions Click below:

[Submit Article](#)