



Studying and Simulation of a Different Formation of U Shape with T and L shapes of Plasmonic Nanoantennas with Variable Substrates



Mohanad Aljanabi^{1,2*} and Yasa Eksioglu¹

¹Department of Electrical and Computer Engineering, Turkey

²Department of Electrical Power Techniques Engineering, Iraq

*Corresponding author: Mohanad Aljanabi, Department of Electrical and Computer Engineering, Istanbul, Turkey, Department of Electrical Power Techniques Engineering, Technical College /Al-Mausaib, Al-Furat Al-Awsat Technical University, Iraq

Submission: 📅 October 05, 2018; Published: 📅 October 30, 2018

Abstract

The optical properties of surface plasmons at the resonant wavelength depend on the geometrical nanostructure of materials, refractive indices, thickness (materials and dielectrics), and shapes of the formation unit cell nanoantennas. In this study, we take different shapes of plasmonic nanoantenna structures with a prototype of single and dual U-shapes as a common part to format a unit cell of nanoantenna by adding T and L-shapes based on a different dielectric such as, a silicon nitride, magnesium fluoride, and aluminium oxide, with gold as a variation of refractive indices. A single U-shape provides a dual spectral resonance at a wavelength range of (500-950)nm. Thus, in these proposed structures, we try to achieve a triple band with the best transmission and field enhancement distributions (electric field intensity and magnetic field intensity), and we design and simulate these fractals by using the 3D- finite difference time domain method Lumerical program with an incident source between a visible to infrared range. From the results, the triple bands have a wide range of applications in medicine as biosensors and in communication systems (optical modulators).

Keywords: Plasmonics; Multi-spectral resonances; Optical properties; Nanoantennas; Geometrical parameters; Variable refractive index

Introduction

Nanoantenna is a nanoparticle of metallic structures designed to deal with light [1,2]. The principles of working such a device is to improve the energy conversion between the nanoantennas and free radiation field [3]. The operation of the nanoantenna takes place successfully in a range between IR to visible so, it has great development designs [4]. A surface Plasmons (SPs) of metallic that is excited by an incident of light has extraordinary effects that have recently become a study focus [5-7]. Currently, nanoantennas are being designed in different shapes and material arrangements [8,9]. The properties of dielectrics have strong effects on LSP (Localized Surface Plasmons), which is important for sensing applications such as optics, biology, and material sciences [10,11] because they depend on localized practical resonances. Thus, it is easy to perform the measurements of (optical parameters) such as absorption, reflection, scattering, and transmission [12-15].

Over the last few years, different shapes of nanoantenna have been proposed by changing arrangement of the parts to obtain multi resonances in a range of mid IR [16] and improve the reflection for spectrometry [17], such as Bowtie [18], loop [19], and triangular [20] as a basic design. On the other hand, there are complicated structures such as the U-shape [21], and SRR (split ring resonator)

[22-24]. Several models of nanoantennas plasmonic have been designed and fabricated by Altug et al that deposit Au and Ti on SiN membrane layers [25,26], while Mosallaei [27] used silver (Ag) based on Silicon substrate [26]. Also, the U-shape is used with other structures such as the Jerusalem Cross (JC) to present multi resonances as perfect metamaterial absorbers (MA) in the THz region. Zarrabi [28] added the U- shape to the H-shape in order to achieve a triple resonance by using the CST program. The arrays of the U-shaped metallic periodic with SRRs to improve the magnetic resonances of metamaterials are composed of high-quality sensing [29].

In this article, we take a different shape of plasmonic nanoantenna structure with a prototype of a single and dual U-shape as a common part to format a unit cell of nanoantenna by adding T and L-shapes of the gold base on a different dielectric such as , SiN ($n=1.98,2,2.16$), MgF_2 ($n=1.37,1.36$) and Al_2O_3 , ($n=1.76$) as a variation of the refractive indices. Consequently, in these proposed structures, we attempt to achieve a triple spectral with the best transmission and field enhancement distributions (electric field intensity (E) and magnetic field intensity (H), we design and simulate these fractals by using the 3D- FDTD method Lumerical program with an incident source between the visible -IR range.

Method of Analysis

In this study Figure 1 shows the different shapes of the Symmetric unit cell of the nanoantenna with geometrical parameters (L, H, W, t) representing the length, height, width, and thickness of the metal respectively, including S the distance between the two shapes in the

same unit cell. The shapes of the nano structures basically depend on the deposition of a gold (Au) layer with ($t=100\text{nm}$) on a substrate, which is variable like SiN, ($n=1.98, 2, 2.16$), MgF_2 , ($n=1.37, 1.36$) and Al_2O_3 , ($n=1.76$), with the dimensions of the unit cell; $L=800\text{nm}$, $H=400\text{nm}$ and $W=(75-100)\text{nm}$.

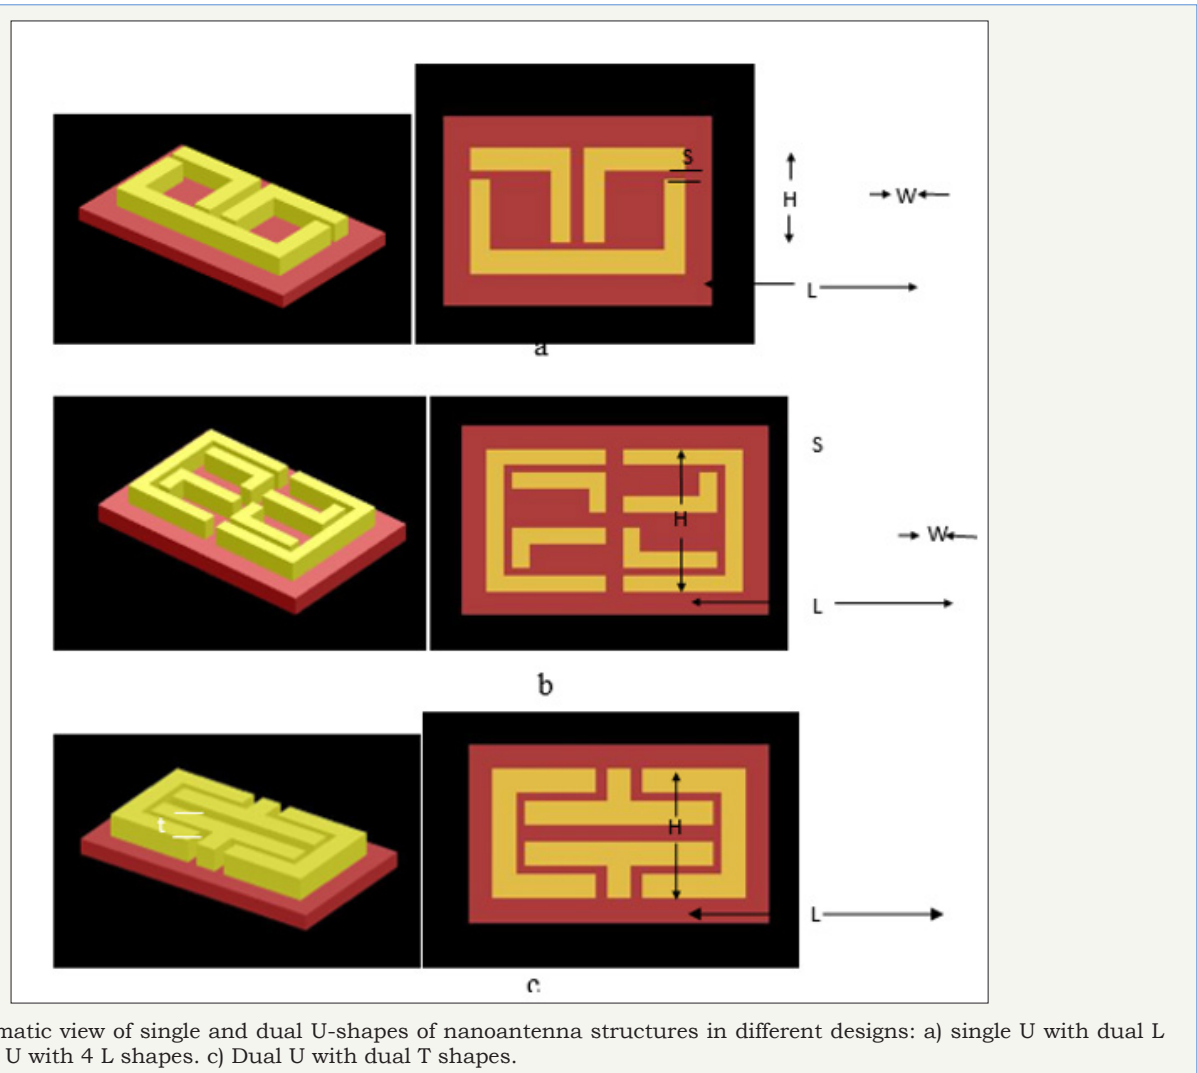


Figure 1: Schematic view of single and dual U-shapes of nanoantenna structures in different designs: a) single U with dual L shapes. b) Dual U with 4 L shapes. c) Dual U with dual T shapes.

Three models of the nano antennas are proposed by using the U-shape added to L, T shapes in a 3D FDTD Lumerical program to design a simulation Plasmonic nanoantenna trying to achieve dual and triple spectral resonance and field enhancement distributions E and H with the best transmission, therefore, we used a multi type of substrate model in order to change the refractive index that effects the surface Plasmon resonance with each a model. We found the values of wave number (k_{sp}) with different values of refractive index and Surface Plasmon frequency (ω_{sp}) from equations (1,2) [30].

$$k_{sp} = \frac{2\pi}{\lambda} \sqrt{\frac{n_m^2 n_d^2}{n_m^2 + n_d^2}} \quad (1)$$

$$\omega_{sp} = \frac{\omega_p}{\sqrt{1 + \epsilon_d}} \quad (2)$$

For Drude models of metal, such as Au or Ag, the dielectric

constant ϵ_m can be written as a function of frequency (ω) from equation (3).

$$\epsilon_m(\omega) = \epsilon_{m,r} + i\epsilon_{m,i} = \epsilon_b - \frac{\omega_p^2}{\omega^2 + \gamma^2} + \frac{i\gamma\omega_p^2}{\omega^3 + \gamma^2\omega} \quad (3)$$

Where $\epsilon_{m,r}$ and $\epsilon_{m,i}$ are real and imaginary parts of the metal's dielectric constant, respectively, ϵ_b is the static term due to the bound charge, and is the damping coefficient [31].

Results and Discussion

Figure 2, shows the results of the simulation of three models (dual U, dual T, a single U dual L, and dual U 4L) with different refractive indices; this work is performed by 3D-FDTD, by a Lumerical solution Inc. The periodic boundary conditions were considered for the x- and y-directions, respectively, and PML boundary condition for z-directions at an incident of an electromagnetic wave in the z-direction.

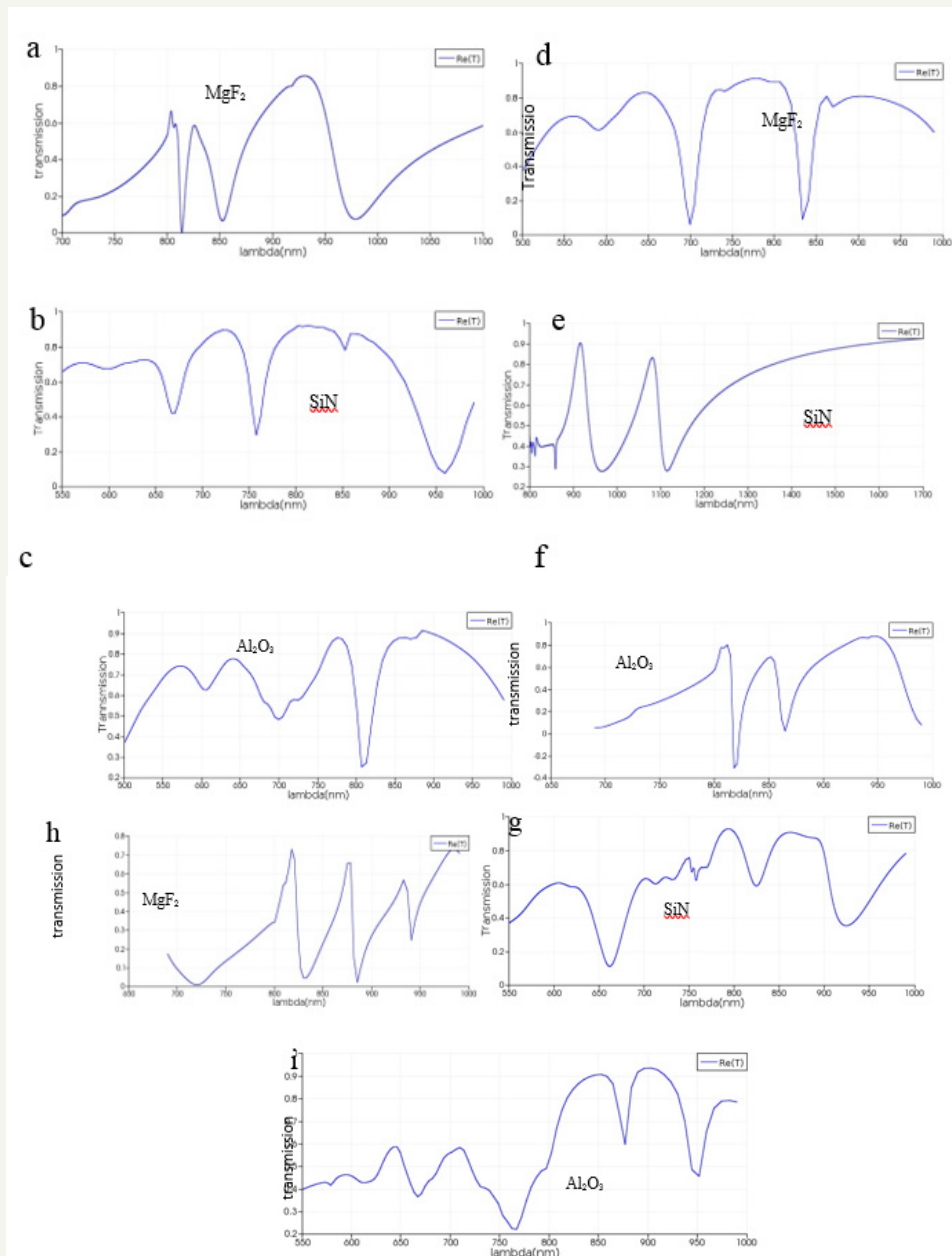


Figure 2: The transmission spectrum Vs wavelength with different refractive indices for the proposed models of plasmonic nano antennas: a, b and c for dual U, dual T. d, e and f for single U, dual L. g, h and i dual U, 4L.

Table 1: The results of the simulation for the three models.

Results of Simulation				
Models	Substrates	Resonances (λ)nm	Range of Wave Length	Transmission
Dual U, dual T (a,b,c)	MgF ₂ (n=1.36)	$\lambda_1=780, \lambda_2=830, \lambda_3=920$	Visible, near IR	0.88
	SiN (n=1.98)	$\lambda_1=720, \lambda_2=830$	Visible, near IR	0.85
	Al ₂ O ₃ (n=1.76)	$\lambda_1=650, \lambda_2=770$	visible	0.9
Single U, dual L (d,e,f)	MgF ₂ (n=1.37)	$\lambda_1=650, \lambda_2=770$	visible	0.84
	SiN (n=2.16)	$\lambda_1=900, \lambda_2=1050$	near IR	0.9
	Al ₂ O ₃ (n=1.76)	$\lambda_1=810, \lambda_2=850$	near IR	0.8
Dual U, 4L (g,h,i)	MgF ₂ (n=1.36)	$\lambda_1=800, \lambda_2=860, \lambda_3=910$	near IR	0.73
	SiN (n=2.16)	$\lambda_1=780, \lambda_2=865$	Visible, near IR	0.92
	Al ₂ O ₃ (n=1.76)	$\lambda_1=850, \lambda_2=900$	near IR	0.94

From Table 1, these models are operated in visible to IR regime and high transmission achieved with the dual U, 4L with Al_2O_3 ($n=1.76$) approximate to 0.94 in near IR, also we obtain high transmission in a visible range with Al_2O_3 and SiN ($n=2.16$) special in a single U and dual L. On the other hand, we can see that there are triple resonances in both designs (Dual U, dual T and Dual U, 4L) with MgF_2 ($n=1.36$) in the same range.

In Figure 3, the field enhancement distributions of E appear strongly with the SiN substrate for all the models in a single U, and a dual L approximate to 0.96 at the center of structure. While the field enhancement distributions of H noticed in the dual U, 4L about 2.62E^{-3} concentrated on both sides of the structure. On the other hand, with Al_2O_3 , H is concentrated at the center with a value 2.01E^{-3} .

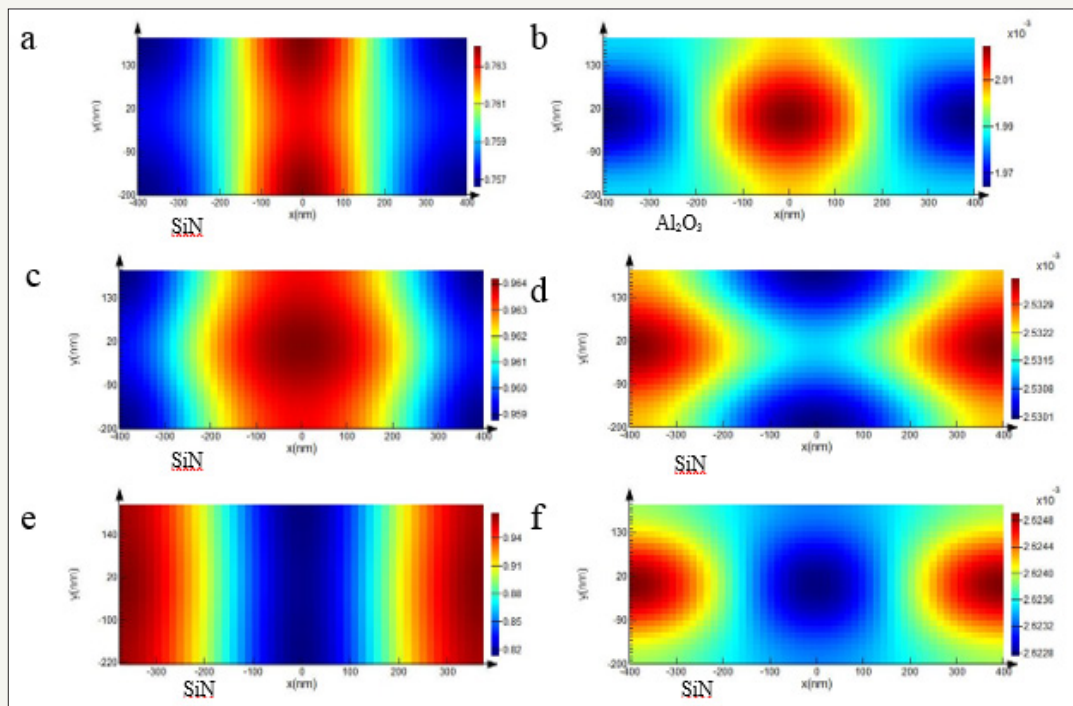


Figure 3: best field distributions of E and H; a and b represent E,H for dual U, dual T. c and d represent E,H for single U, dual L. e and f represent E,H for dual U, 4L.

Conclusion

As a result of the interaction between the incident light with the surface of the metals, each model demonstrates that dielectric and refractive index and also the thickness of the substrate have an effect on radiation efficiency. High transmission and field enhancements show a distribution that is related to the effect of the positions of the surface plasmons which reveals them to be a good candidate for biosensor applications. These models offer flexibility and a wide range of designing and fabrication structures and optimizing the response of surface Plasmon at visible and near the IR regime. The proposed different shape of models of nanoantenna plasmonic can also support dual and triple response resonances of operations and act as a high transmitted for new devices. Through these results, we can find some methods for new arrangements to enhance plasmonic nanoantennas quality and accuracy.

References

- Schuck PJ, Fromm DP, Sundaramurthy A, Kino GS, Moerner WE (2005) Improving the mismatch between light and nanoscale objects with gold bowtie nanoantennas. *Phys Rev Lett* 94(1): 17402.
- Crozier KB, Sundaramurthy A, Kino GS, Quate CF (2003) Optical antennas: resonators for local field enhancement. *J Appl Phys* 94: 4632-4642
- Xu J, Kumar A, Chaturvedi P, Hsu KH, Fang NX (2010) Enhancing light coupling with plasmonic optical antennas, in metamaterials: theory, design, and applications. In: Cui TJ, Smith D, Liu R, Springer, NY, USA.
- Kabashin AV, Evans P, Pastkovsky S, Hendren W, Wurtz GA, et al. (2009) Plasmonic Nano rod metamaterials for biosensing. *Nature Materials* 8: 867.
- Bozhevolnyi SI, Sndergaard T (2003) General properties of slow-plasmon resonant nanostructures: nano-antennas and resonators. *Phys Rev Lett* 91: 253902.
- Barnard ES, White J, Chandra A, Brongersma ML (2008) Spectral properties of plasmonic resonator antennas. *Opt Express* 16: 16529-16537.
- Biagioni P, Huang JS, Duqo L, Finazzi M, Hecht B (2009) Cross resonant optical antenna. *Phys Rev Lett* 102(25): 256801.
- Bakker RM, Drachev VP, Yuan HK, Shalaev VM (2003) Enhanced transmission in near field imaging of layered plasmonic structures. *Phys Rev Lett* 91: 227402.
- Abe M, Suwa T (2004) Surface plasma resonance and magneto-optical enhancement in composites containing multi core-shell structured nanoparticles. *Phys Rev B* 70(23): 235103.
- Zhu J, Sun Z, Li JJ, Zhao JW (2010) Local temperature pattern in plasmonic gold nano shell: tuning the heat generation. *Eur Phys J B Condens Matter Complex Syst* 78(3): 311-314.
- Haes AJ, Zou S, Schatz GC, Duyn RPV (2004) Nanoscale optical biosensor: short range distance dependence of the localized surface Plasmon resonance of noble metal nanoparticles. *J Phys Chem B* 108(22): 6961-6968.

12. Raschke G, Kowarik S, Franzl T, Snnichsen C, Klar TA, et al. (2003) Bimolecular recognition based on single gold nanoparticle lightscattering. *Nano Letters* 3(7): 935-938.
13. Smyth EJ, Dickey MD, Boa J, Whiteside's GM, Capasso F (2009) Optical antenna arrays on a fiber facet for in situ surface-enhanced Raman scattering detection. *Nano Letters* 9(3): 1132-1138.
14. Liu N, Mesch M, Weiss T, Hatchel M, Giessen H (2010) Infrared perfect absorber and its application as plasmonic sensor. *Nano Letters* 10(7): 2342-2348.
15. Liu N, Tang ML, Hatchel M, Giessen H, Alivisatos AP (2011) Nanoantenna enhanced gas sensing in a single tailored nano focus. *Nature Materials* 10(8): 631-636.
16. Turkmen M, Aksu S, Cetin AE, Yanik AA, Altug H (2011) Multi-resonant metamaterials based on UT-shaped nano-aperture antennas. *Opt Express* 19: 7921-7928.
17. Adato R, Yanik AA (2011) On chip plasmonic monopole nano-antennas and circuits. *Nano Lett* 11(12): 5219-5226.
18. Chen CK, Chang MH, Wu HT, Lee YC, Yen TJ (2014) Enhanced vibrational spectroscopy, intracellular refractive indexing for label-free biosensing and bio imaging by multiband plasmonic-antenna array. *Biosens Bioelectron* 60: 343-350.
19. Ahmadian D, Ghobadi C, Nourinia J (2013) Ultra-compact two-dimensional plasmonic nano-ring antenna array for sensing applications. *Opt Quantum Q4 Electron*, pp.1-10.
20. Giloon M, Astilean S (2014) Negative index optical chiral metamaterials based on asymmetric hexagonal arrays of metallic triangular nano prisms. *Opt Commun* 315: 122-129.
21. Turkmen M, Serap A, Cetin AE, AliYanik A, Altug H (2011) Multi-resonant metamaterials based on UT-shaped nano-aperture antennas. *Opt Express* 19(8): 7921-7928.
22. Horikawa J, Kawakami A, Hyodo M, Tanaka S, Takeda M, et al. (2014) Evaluation of nano-slot antenna for mid-infrared detectors. *Infrared Phys Technol* 67: 21-24.
23. Giessen H, Lippitz M (2010) Directing light emission from quantum dots. *Science* 329(5994): 910-911.
24. Acuna GP, Möller FM, Holzmeister P, Beater S, Lalkens B, et al. (2012) Fluorescence enhancement at docking sites of DNA-directed self-assembled nanoantennas. *Science* 338(6106): 506-510.
25. Cetin AE, Turkmen M, Aksu S, Etezadi D, Altug H (2015) Multi-resonant compact nano aperture with accessible large near fields. *Appl Phys B* 118(1): 29-38.
26. Ahmadi A, Mosallaei H (2010) Plasmonic nano loop array antenna. *Opt Lett* 35(21): 3706-3708.
27. Fsaneh SA, Ferdows BZ, Samaneh H, Navid PG (2015) Independent polarization and multi-band THz absorber base on Jerusalem cross. *Optics Communications* 352: 121-126.
28. Ferdows BS (2017) Sub wavelength plasmonic nano-antenna with H and U shape for enhancement of multi resonance. *Optik* 127(10): 4490-4494.
29. Chen J, Fan W, Zhang T, Tang C, Ying (2017) Engineering the magnetic plasmon resonances of metamaterials for high-quality sensing. *Optics Express* 25(4): 3675.
30. Maier S (2007) *Plasmonics*. Springer, New York, USA, p. 254.
31. Tumkur T, Barnakov Y, Kee ST, Noginov MA, Lieberman V (2015) Permittivity evaluation of multi-layered hyperbolic metamaterials: Ellipsometry vs. reflectometry. *Journal of Applied Physics* 117: 103104.



Creative Commons Attribution 4.0 International License

For possible submissions Click Here

Submit Article



Research & Development in Material Science

Benefits of Publishing with us

- High-level peer review and editorial services
- Freely accessible online immediately upon publication
- Authors retain the copyright to their work
- Licensing it under a Creative Commons license
- Visibility through different online platforms