



Ordered Defects: A Path to High-Temperature Superconductivity and Magnetic Order



Pablo DE*

Faculty of Physics and Earth Sciences, Germany

*Corresponding author: Pablo DE, Faculty of Physics and Earth Sciences, Germany

Submission: 📅 November 06, 2018; Published: 📅 November 29, 2018

Introduction

Defects in the atomic lattice of solids are sometimes desired. For example, atomic vacancies, single ones or more elaborated defective structures, can generate localized magnetic moments in a non-magnetic crystal lattice. Increasing their density to a few percent, magnetic order appears. Furthermore, certain interfaces can give rise to localized two-dimensional superconductivity with a broad range of critical temperatures. Old and new experimental facts emphasize the need to join "ordered defects" in solids to achieve room temperature superconductivity and magnetic order.

Magnetic and superconducting orders at room temperature are highly desirable due to possibilities to apply these phenomena in devices at normal life conditions, apart from the huge basic research interest. Although magnetic order is found at 300K in a not so large list of materials, superconductivity at room temperature appeared to be much more difficult to find. Here, we would like to emphasize that ordered defects in some lattice structures can provide us a path to reach both phenomena at very high temperatures in materials that do not show them in their defect free state. We would like to pay attention here on two cases of lattice defects in solids. Namely, a single or a group of vacancies and two dimensional (2D) well defined interfaces in some specific atomic lattices.

Vacancies can trigger a magnetic moment around its position in the atomic lattice. A large number of experimental and theoretical work has been done in this respect. For example, STM local measurements revealed that C-vacancies, produced by low energy ion irradiation at the surface of graphite, have a local magnetic moment [1]. Having a large enough density (5%) of hydrogen (or protons) or C-vacancies at certain positions [2,3], one can show experimentally that magnetic order at room temperature appears in graphite bulk samples. Several studies with techniques like element specific X-ray magnetic circular dichroism (XMCD) [4,5], NMR [6], magnetization and transport [7] indicate that the magnetic order triggered by defects is intrinsic and with Curie temperatures clearly above 300K. In the case of graphite [5] or ZnO [8,9], XMCD results indicate that the valence band is spin polarized in a relative large energy range, an apparently general feature in materials that show defect induced magnetism (DIM).

Due to the rather simple way to trigger in non-magnetic materials, room temperature magnetic order by low energy ion irradiation, we may ask whether some kind of devices have been already proposed. Two recent examples are worth mentioning. The first is the spin layer that occurs at the interface between magnetic and non-magnetic regions of the same material, ZnO:Li in the reported case [10]. Whereas the magnetic path of the oxide micro- or nanostructure is produced by an inexpensive 300eV proton irradiation plasma chamber, the protected non-magnetic semiconducting regions act as a potential well for the thermally activated conduction electrons. The interfaces between magnetic and non-magnetic regions do produce a giant positive magnetoresistance, in contrast to the small and negative magnetoresistance of the magnetic paths alone. This characteristic and other details of the homo-junctions open up a new and simple way to use the spin splitting created in the irradiated oxide for spintronic devices.

Other unexpected result was obtained recently by low-energy ion irradiation on TiO₂. After a gentle ion irradiation hence, the originally non-magnetic TiO₂ becomes magnetic at room temperature due to Ti divacancies (which are stable at room temperature) and with the magnetization vector normal to the main area of the TiO₂ [11]. The rather large magnetic anisotropy is related apparently to the fact that the magnetic layer resides at the very near surface region. Further increase of the amount of defects by subsequent ion irradiation, vanishes the magnetic anisotropy. Recently obtained results [12] indicate that should be possible to produce nanostructured areas of TiO₂ with perpendicular magnetic anisotropy. Low energy ion irradiation and the existence of DIM in several oxides may open up a new method to reach perpendicular magnetic anisotropy by far simpler and economically advantageous than several others used nowadays [13].

Let us now discuss the other order phenomenon that appears at a specially ordered lattice defect, namely at certain 2D interfaces. Systematically done STM studies of graphene bilayers showed the existence of Van Hove singularities in the electronic density of states that shift to lower bias voltages the smaller the twist angle between the graphene layers [14]. As emphasized recently Figure

1. Normalized resistance vs. temperature at constant magnetic fields applied normal to the graphene planes and interfaces of the

Following samples:

- Nature graphite sample; data taken from Figure 1a [14].
- Bilayer graphene device M_2 (twist angle=1:05), data taken from Figure 1b [15,16].

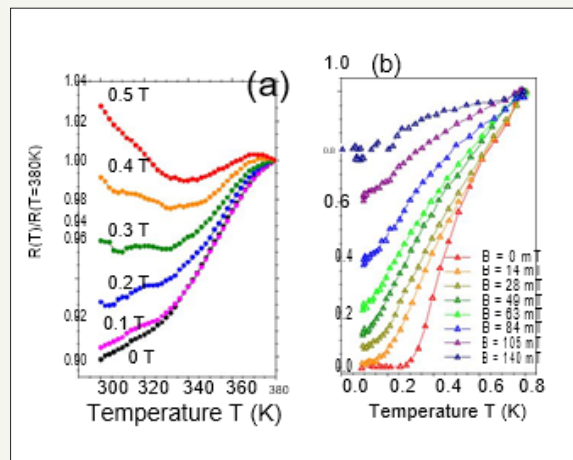


Figure 1: Normalized resistance vs. temperature at constant magnetic fields applied normal to the graphene planes and interfaces of the following samples:

Figure 1a: Nature graphite sample; data taken from Figure 1a [14].

Figure 1b: Bilayer graphene device M_2 (twist angle=1:05), data taken from Figure 1b in [15].

By Volovik [17] the Van Hove singularities are related to the attending of the electronic energy band at well defined regions, which can be localized through the measured more pattern in the electronic spectrum. This appears to be the reason for the existence of superconductivity found recently in bilayer graphene with critical temperatures around 1K [15]. We may ask now, whether well-ordered bulk graphite samples have similar 2D interfaces. The answer is yes, indeed, and the experimental evidence is overwhelming. More patterns in the electronic spectrum measured by STM due to misoriented graphene layers of the graphite structure were found already in 1990, at the surface of a graphite HOPG bulk sample [18,19]. Their influence on the measured conductivity was not, however, realized till 2008 [20,21]. There are two more 2D interfaces that can appear parallel to the graphene planes in real graphite samples, namely:

- The one between regions with Bernal and rhombohedral (RH) stacking orders, twisted or untwisted, and
- Between twisted RH regions. The existence of the minority RH stacking phase was concerned in a large number of graphite bulk samples by XRD studies [14] and it's in hence in the conductivity was recently reported [22].

Superconductivity at these interfaces is expected to appear at very high temperatures due to the existence of a dispersion less electron band, a so called at band [17]. This at band has been predicted to exist at, e.g., the surface of graphite with RH stacking order [17,23] or at the 2D interface between Bernal and RH stacking orders [24]. Its existence was concerned experimentally at the surface of small and thin RH patches surrounded by regions with Bernal stacking order [25]. It is interesting to compare the superconducting transitions identified in the temperature

dependence of the Figure 2a: Temperature dependence of the resistance or voltage (at constant current) measured in the bilayer graphene device M_2 (red line, taken from Figure 1b in [15], bottom-left axes) and lamella L3 (black line, taken from in [23], upper-right axes). Characteristic voltage-current curves at constant temperatures obtained in the same samples shown in Figure 1a. The data of lamella L3 (black line) were taken from [23] (upper-right axes) and from the bilayer graphene device (red line) from Figure 1a in [15] (bottom-left axes).

Electrical resistance at constant applied ends in a bilayer graphene [15] and the one reported two years before in several bulk samples with internal interfaces [14]. Figure 1 shows the two sets of normalized resistance data for a better comparison. As discussed in [14] the back-ground resistance in Figure 1a is simply because the voltage electrodes do not touch the interface(s) of interest. Both transitions show some similarities worth mentioning, in spite of the two orders of magnitude difference in temperature. Namely, there is not a simple shift of the transition to lower temperatures with magnetic field, but a small applied field already prevents a complete superconducting path between the voltage electrodes. Although in the case of the bulk graphite sample Figure 1a one would tend to explain this fact by an extra magneto resistance coming from the background resistance, this does not seem to be the reason for the bilayer device.

Whereas in the case of the bulk graphite sample the transition hardly shifts to lower temperatures under an applied magnetic field (in the measured field region), the broadness of the transitions in the bilayer prevents a clear determination of a temperature dependent upper critical field $B_{c_2}(T)$. The overall results suggest the existence of granular superconductivity in both samples. In other words, neither in the bilayer nor in the internal interfaces of the

bulk sample a homogeneous superconducting region between the voltage electrodes exists but superconducting patches. A magnetic field influences the (Josephson) coupling between those patches and therefore no zero resistance path between the electrodes remains. In spite of granular superconductivity, at low enough fields permanent current paths can exist, the reason for us trapping [26,27] and the remnant resistance observed after removing the applied field [14]. Future studies should clarify whether the granular superconductivity is intrinsic or extrinsic due to defects (or inhomogeneous doping) at the interfaces or in the bilayer graphene. The Josephson response between superconducting patches that exist within the embedded interfaces in bulk graphite samples, can be measured by depositing electrodes directly at the edges of the interfaces, as has been done using TEM lamellae in [23].

Let us compare the results published in 2013 of one of those TEM lamellae with one of the bilayer graphene devices published recently. Figure 2a shows the temperature dependence of the resistance of device M2, see Figure 1b [15], and of the voltage (measured at constant current) of the lamella L3, see in [23]. Note that the transition observed in the lamella does not represent necessarily the critical temperature of the superconducting patches but the temperature where the Josephson coupling gets robust enough to influence the measured voltage. The Josephson response was identified by measuring current-voltage characteristics in both samples shown in Figure 2b at two temperatures. The Josephson characteristics curves measured in sample L3 at higher temperatures [23] are also similar to those measured in the M2 device [15] and can be very well understood following the Ambegaokar & Halperin [28] model.

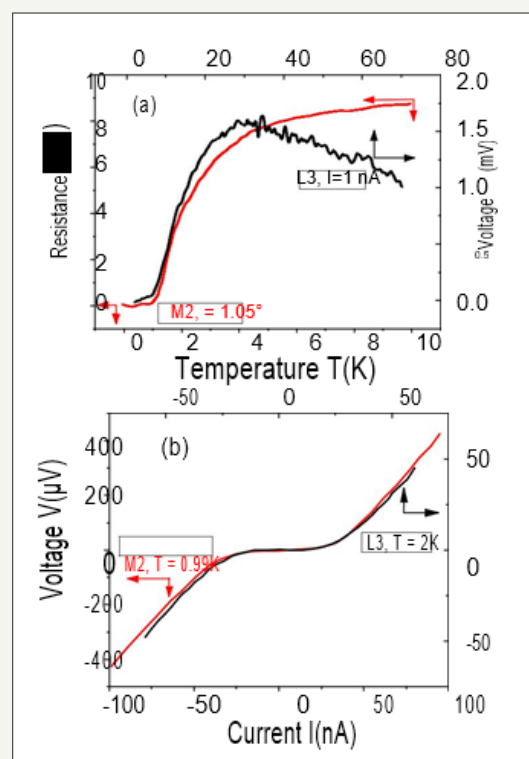


Figure 2:

Figure 2a: Temperature dependence of the resistance or voltage (at constant current) measured in the bilayer graphene device M2 (red line, taken from Figure 1b in [15], bottom-left axes) and lamella L3 (black line, taken from [23], upper-right axes).

Figure 2b: Characteristic voltage-current curves at constant temperatures obtained in the same samples shown in Figure 2a. The data of lamella L3 (black line) were taken from [23] (upper-right axes) and from the bilayer graphene device (red line) from [15] (bottom-left axes).

The clear similarities between the reported measurements in [15,23] make any further comment superfluous. Future experiments should try to localize and characterize in bulk graphite samples the interfaces with higher critical temperatures in order to hopefully start their difficult but necessary production. Finally, we note that there are several examples in literature on the existence of superconductivity at 2D interfaces, apart from the interesting cases found in oxides [29,30]. Remarkable is the superconductivity

found at the interfaces of pure Bi (a material with some similarities to graphite) and BiSb bi-crystals up to critical temperatures 21K [31-34]. Moreover, dislocations at certain interfaces of semiconducting superlattices are thought to trigger superconductivity up to 6K [35,36], an idea that has been also proposed for graphite [37]. Strain induced superconductivity at interfaces of semiconducting layers has been treated theoretically based on the influence of partial bands [38].

Acknowledgement

We are grateful to Ballestar A for discussions and a carefully reading of the manuscript. Fruitful discussions with M Stiller and J Barzola-Quiquia on their unpublished magnetic force microscopy data on TiO₂ lms are gratefully acknowledge. We acknowledge the help of C Precker for digitalizing the data of Figure 1b.

References

- Ugeda MM, Brihuega I, Guinea F, Rodriguez JM (2010) Missing atom as a source of carbon magnetism. *Phys Rev Lett* 104: 096804.
- Yazyev OV (2010) Emergence of magnetism in graphene materials and nanostructures. *Rep Prog Phys* 73: 056501.
- Yazyev OV (2016) Theory of magnetism in graphitic materials. In: Esquinazi P (Ed.), Springer International Publishing, Switzerland, 1: 24.
- Ohldag H, Tyliczszak T, Hohne R, Spemann D, Esquinazi P, et al. (2007) Surface nucleation in the freezing of gold nanoparticles. *Phys Rev Lett* 98: 187204.
- Ohldag H, Esquinazi P, Arenholz E, Spemann D, Rothermel M, et al. (2010) The role of hydrogen in room-temperature ferromagnetism at graphite surfaces. *New Journal of Physics* 12: 123012.
- Freitas JCC, Scopel WL, Paz WS, Bernardes LV, Filho FE, et al. (2015) Determination of the hyperfine magnetic field in magnetic carbon-based materials: DFT calculations and NMR experiments. *Scientific Reports* 5: 14761.
- Spemann D, Esquinazi P (2016) Evidence for magnetic order in graphite from magnetization and transport measurements. In: Esquinazi P (Ed.), *Basic Physics of Functionalized Graphite*, Switzerland, pp. 45-76.
- Herng TS, Qi DC, Berlijn T, Yi JB, Yang KS, et al. (2010) Room-temperature ferromagnetism of Cu-doped ZnO films probed by soft x-ray magnetic circular dichroism. *Phys Rev Lett* 105: 207201.
- Lorite I, Straube B, Ohldag H, Kumar P, fuerte VM, et al. (2015) *Applied Physics Letters* 106: 082406.
- Botsch L, Lorite I, Kumar Y, Esquinazi P, Michalsky T, et al. (2017) Spin-filter effect at the interface of magnetic/non-magnetic homojunctions in Li doped ZnO nanostructures.
- Stiller M, Barzola Quiquia J, Esquinazi P, Spemann D, Meijer J, et al. (2016) *AIP Advances* 6: 125009.
- Stiller M, Barzola Quiquia J. Private communication.
- Tudu B, Tiwari A (2017) *Vacuum*, pp. 146-329.
- Precker CE, Esquinazi PD, Champi A, Barzola Quiquia J, Zoraghi M, et al. (2016) Identification of a possible superconducting transition above room temperature in natural graphite crystals. *New J Phys* 18: 113041.
- Cao Y, Fatemi V, Fang S, Watanabe K, Taniguchi T, et al. (2018) Unconventional superconductivity in magic-angle graphene superlattices. *Nature* 556: 43-50.
- Brihuega I, Mallet P, Herrero GH, Laissardiere GT, Ugeda MM, et al. (2012) Unraveling the intrinsic and robust nature of van Hove singularities in twisted bilayer graphene by scanning tunneling microscopy and theoretical analysis. *Phys Rev Lett* 109: 196802.
- Volovik GE (2018) Graphite, graphene and the flat band superconductivity. *JETP Letters* 107: 516.
- Kuwabara M, Clarke DR, Smith AA (1990) *Appl Phys Lett* 56: 2396.
- Miller DL, Kubista KD, Rutter GM, Ruan M, Heer WA, et al. (2010) Structural analysis of multilayer graphene via atomic moiré interferometry. *Phys Rev B* 81: 125427.
- Esquinazi PD, Lysogorskiy Y (2016) Experimental evidence for the existence of interfaces in graphite and their relation to the observed metallic and superconducting behavior. In: Esquinazi P (Ed.), *Basic physics of functionalized graphite*, Springer International Publishing, Switzerland, pp. 145-179.
- Zoraghi M, Quiquia JB, Stiller M, Esquinazi PD, Estrela Lopis I (2018) *Carbon* 139: 1074.
- Zoraghi M, Barzola QJ, Stiller M, Setzer A, Esquinazi P, et al. (2017) Influence of rhombohedral stacking order in the electrical resistance of bulk and mesoscopic graphite. *Phys Rev B* 95: 045308.
- Ballestar A, Barzola Quiquia J, Scheike T, Esquinazi P (2013) Josephson-coupled superconducting regions embedded at the interfaces of highly oriented pyrolytic graphite. *New J Phys* 15: 023024.
- Kopnin NB, Heikkilä TT, Volovik GE (2011) High-temperature surface superconductivity in topological flat-band systems. *Phys Rev B* 83: 220503.
- Munoz WA, Covaci L, Peeters F (2013) Tight-binding description of intrinsic superconducting correlations in multilayer graphene. *Phys Rev B* 87: 134509.
- Pierucci D, Sediri H, Hajlaoui M, Girard JC, Brumme T, et al. (2015) Evidence for flat bands near the Fermi level in epitaxial rhombohedral multilayer graphene. *ACS Nano* 9: 5432-5439.
- Stiller M, Esquinazi PD, Quiquia JB, Precker CE (2018) *J Low Temp Phys* pp. 191-105.
- Ambegaokar V, Halperin BI (1969) Voltage due to thermal noise in the dc Josephson effect. *Phys Rev Lett* 22: 1364.
- Mohanta N, Taraphder A (2014) Phase segregation of superconductivity and ferromagnetism at the LaAlO₃/SrTiO₃ interface. *J Phys Condens Matter* 26(2): 025705.
- Boschker H, Manske D, Mannhart J (2016) *Physik Journal* pp. 15-37.
- Gitsu DV, Grozav AF, Kistol VG, Leporda LI, Muntyanu FM (1992) Experimental observation of a superconducting phase with T_c ~ 8.5K in large-angle bismuth bicrystals. *JETP Lett* 55: 403.
- Muntyanu FM, Leporda LI (1995) *Phys Solid State* 37: 298.
- Muntyanu FM, Gilewski A, Nenkov K, Zaleski AJ, Chistol V (2007) Fermi-surface rearrangement in Bi bicrystals with twisting superconducting crystallite interfaces. *Phys Rev B* 76: 014532.
- Muntyanu F, Gilewski A, Nenkov K, Zaleski A, Chistol V (2008) *Solid State Communication* pp. 147-183.
- Fogel NY, Pokhila AS, Bomze YV, Sipatov AY, Fedorenko I, et al. (2001) Novel superconducting semiconducting superlattices: dislocation-induced superconductivity? *Phys Rev Lett* 86: 512.
- Fogel NY, Buchstab EI, Bomze YV, Yuzepovich OI, Mikhailov MY, et al. (2006) Direct evidence for interfacial superconductivity in two-layer semiconducting heterostructures. *Phys Rev B* 73: 161306.
- Esquinazi P, Heikkilä TT, Lysogorskiy YV, Tayurskii DA, Volovik GE (2014) On the superconductivity of graphite interfaces. *JETP Letters* 100: 336-339.
- Tang E, Fu L (2014) Strain-induced partially flat band, helical snake states and interface superconductivity in topological crystalline insulators. *Nature Physics* 10: 964-969.



Creative Commons Attribution 4.0
International License

For possible submissions Click Here

Submit Article



Research & Development in Material Science

Benefits of Publishing with us

- High-level peer review and editorial services
- Freely accessible online immediately upon publication
- Authors retain the copyright to their work
- Licensing it under a Creative Commons license
- Visibility through different online platforms