


# The Mechanism of Self-Reactivation of Cao-Based CO<sub>2</sub> Adsorbents

Sufang Wu\*, Fanfeng Pan, Hao Liu and Peiqiang Lan

College of Chemical and Biological Engineering, China

ISSN: 2576-8840

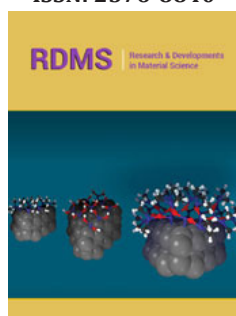

\*Corresponding author: Sufang Wu, College of Chemical and Biological Engineering, China

Submission:  May 06, 2019

Published:  May 13, 2019

Volume 10 - Issue 5

**How to cite this article:** Sufang W\*, Fanfeng P, Hao Liu, Peiqiang L. The Mechanism of Self-Reactivation of Cao-Based CO<sub>2</sub> Adsorbents. Res Dev Material Sci. 10(5).RDMS.000747.2019. DOI: [10.31031/RDMS.2019.10.000747](https://doi.org/10.31031/RDMS.2019.10.000747)

**Copyright@** Sufang Wu, This article is distributed under the terms of the Creative Commons Attribution 4.0 International License, which permits unrestricted use and redistribution provided that the original author and source are credited.


## Abstract

The self-reactivation phenomenon of CaO-based CO<sub>2</sub> adsorbents produced by high-temperature thermal pretreatment improves the durability of adsorbents in calcium looping process. The self-reactivation mechanisms of limestone and Nano-CaO-based adsorbents were explained as the conversion of hard skeleton to soft skeleton and the formation of cracks between Nano-grains respectively. The summarization of the recent researches about the triggering conditions is to provide reference for grasping and utilizing the self-reactivation of adsorbents.


**Keywords:** CO<sub>2</sub> adsorption; Calcium looping; CaO-based adsorbent; Self-reactivation

## Mini Review

Calcium looping (CaL) includes carbonation and regeneration process (Equation 1) has a wide use in flue gas and chemical process for CO<sub>2</sub> capture [1-4]. Improving the cyclic stability of CaO-based adsorbents is a research hotspot in this field. Many researches focused on optimizing the pore structure [5-8], doping additives [9-11] and improving the skeleton stability of CaO-based adsorbents to reduce sintering [12].



Manovic et al. [11]; [13,14] found that limestone exhibited an abnormal 'self-reactivation phenomenon' after thermal pretreatment at 900-1200 °C for 6-48h, in which the sorption capacity of the adsorbent rose with the increasing of initial cycle number (Figure 1). They proposed a 'pore skeleton' model to explain the mechanism of self-reactivation of limestone (Figure 2); [13]. The external skeleton in adsorbents which could react with CO<sub>2</sub> was defined as 'soft skeleton' and the internal skeleton without carbonation was defined as 'hard skeleton'. The pre-calcination enhanced sintering of the nascent CaO soft skeleton and the formation of a hard skeleton. During the subsequent CaL cycles, part of CaO in the hard skeleton could be converted into soft skeleton due to the deep carbonation reaction, which caused the increase in the number of active sites. It can be concluded that the self-reactivation mechanism of limestone is the conversion of hard skeleton to soft skeleton in adsorbents.

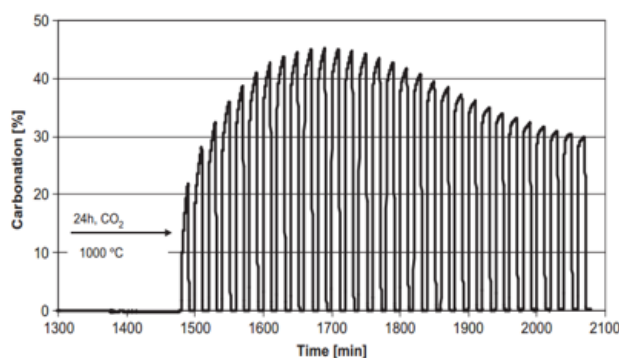

**Figure 1:** The self-reactivation phenomenon of limestone [11].

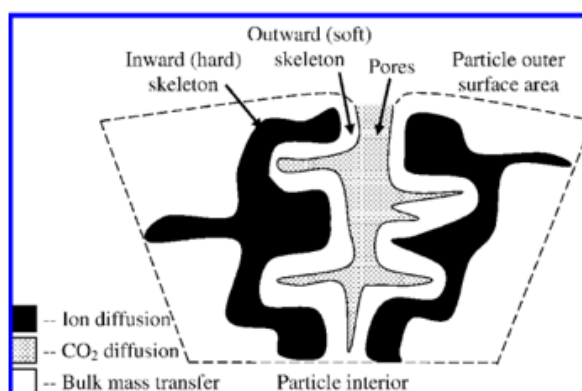


Figure 2: Pore-skeleton model of the self-reactivation mechanism of limestone [13].

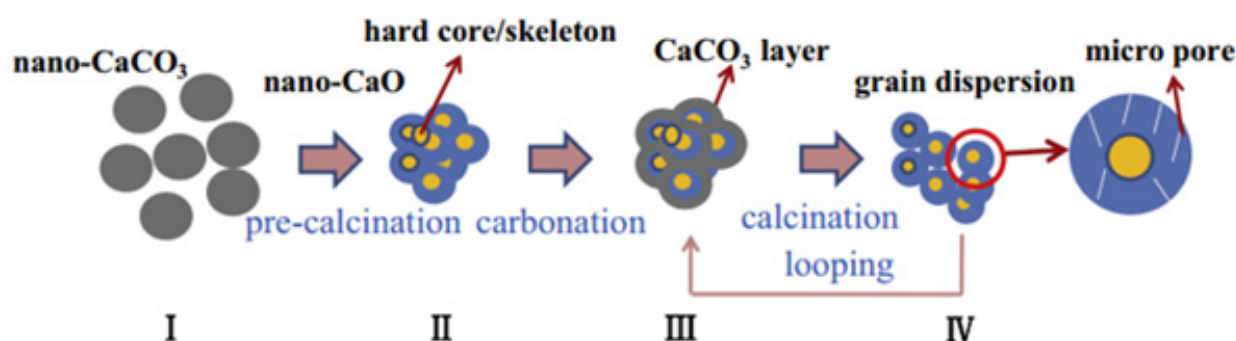


Figure 3: Grain-core-pore model of the self-reactivation mechanism of nano-CaO-based adsorbents [15].

The self-reactivation mechanism of Nano-CaO-based adsorbents is different from that of limestone due to the different size of calcium precursors. S.F. Wu et al. [15] proposed a 'grain-core-pore' model to explain the self-reactivation mechanism of Nano-CaO-based adsorbents (Figure 3). After nano-CaCO<sub>3</sub> (I) was pre-calcined at high temperature for a prolonged period, the Nano-CaO particles were sintered and accumulated into larger particles with a hard core (II). During the first carbonation, larger CaO particles (II) were carbonated with CO<sub>2</sub> and the reaction formed a thick CaCO<sub>3</sub> layer (III). At the subsequent calcination stage, the decomposition of CaCO<sub>3</sub> layer led to the release of CO<sub>2</sub> and the return of part of Nano-CaO grains (IV), thereby increasing the number of active sites. In summary, the self-reactivation mechanism of Nano-CaO-based adsorbents is the formation of cracks between Nano-grains.

Based on these mechanism models, there are many researches focusing on the triggering conditions for self-reactivation of adsorbents. First, the self-reactivation triggering of the limestone adsorbent required severer thermal pretreatment operation conditions (high temperature, long time and CO<sub>2</sub> atmosphere) to bring more hard skeletons [11], while the Nano-CaO-based sorbent was not resistant to sintering, requiring milder thermal pretreatment conditions [16]. Moreover, the increase of carbonation temperature and the prolongation of carbonation time as well as

the reduction in the regeneration temperature were beneficial to the self-reactivation triggering of adsorbents [15]. Finally, the anti-sintering dopant was favorable for the self-reactivation triggering of adsorbents [13,15].

The self-reactivation phenomenon of CaO-based adsorbents induced by thermal pretreatment can effectively improve the sorption stability of adsorbents in CaL process, which has a practical application value. However, there are still some shortcomings in the recent studies of self-reactivation of CaO-based adsorbents. First, the reason for different effects brought by different kinds of dopants is not clear. Besides, in addition to focusing on the self-reactivation triggering conditions, there are few researches paying close attention to what factors affect the self-reactivation performance, which includes the degree of increase in sorption capacity during self-reactivation and the cyclic stability after self-reactivation.

## References

1. Rogelj J, Meinshausen M, Knutti R (2012) Global warming under old and new scenarios using IPCC climate sensitivity range estimates. *Nat Clim Change* 2(4): 248-253.
2. Shimizu T, Hirama T, Hosoda H, Kitano K, Inagaki M, et al. (1999) A twin fluid-bed reactor for removal of CO<sub>2</sub> from combustion processes. *Chen Eng Res Des* 77(1): 62-68.

3. Ridha FN, Lu DY, Symonds RT, Champagne S (2016) Attrition of CaO-based pellets in a 0.1MWth dual fluidized bed pilot plant for post-combustion CO<sub>2</sub> capture. *Powder Technol* 291: 60-65.
4. Wu SF, Li QH, Kim JN, Yi KB (2008) Properties of a nano CaO/Al<sub>2</sub>O<sub>3</sub> CO<sub>2</sub> sorbent. *Ind Eng Chem Res* 47: 180-184.
5. Alvarez D, Abanades JC (2005) Pore size and shape effects on the recarbonation performance of calcium oxide submitted to repeated calcination/recarbonation cycles. *Energ Fuel* 19: 270-278.
6. Jiang L, Hu S (2016) Performance and carbonation kinetics of modified CaO-based sorbents derived from different precursors in multiple CO<sub>2</sub> capture cycles. *Energ Fuel* 30(11): 9563-9571.
7. Guo HX, Yan SL, Zhao YJ, Ma XB, Wang SP (2019) Influence of water vapor on cyclic CO<sub>2</sub> capture performance in both carbonation and decarbonation stages for Ca-Al mixed oxide. *Chem Eng J* 359(1): 542-551.
8. Hu Y, Liu W, Sun J (2016) Structurally improved CaO-based sorbent by organic acids for high temperature CO<sub>2</sub> capture. *Fuel* 167: 17-24.
9. Azimi B, Tahmasebpour M, Jimenez PE, Perejon A, Valverde JM (2019) Multicycle CO<sub>2</sub> capture activity and fluidizability of Al-based synthesized CaO sorbents. *Chem Eng J* 358: 679-690.
10. Ping HL, Wang Y, Wu SF (2016) Preparation of MgO-coated nano CaO using adsorption phase reaction technique for CO<sub>2</sub> sorption. *RSC Advances* 6(47): 41239-41246.
11. Manovic V, Anthony EJ, Loncarevic D (2009) CO<sub>2</sub> looping cycles with CaO-based sorbent pretreated in CO<sub>2</sub> at high temperature. *Chem Eng Sci* 64(14): 3236-3245.
12. Bazaikin YV, Malkovich EG, Derevschikov VS, Lysikov AI, Okunev AG (2016) Evolution of sorptive and textural properties of CaO-based sorbents during repetitive sorption/regeneration cycles. *Chem Eng Sci* 152: 709-716.
13. Manovic V, Anthony EJ (2008) Thermal activation of CaO-based sorbent and self-reactivation during CO<sub>2</sub> capture looping cycles. *environ. Sci Technol* 42(11): 4170-4174.
14. Manovic V, Anthony EJ (2009) CaO-based pellets supported by calcium aluminate cements for high-temperature CO<sub>2</sub> capture. *Environ Sci Technol* 43(18): 7117-7122.
15. Lan PQ, Wu SF (2015) Mechanism for self-reactivation of nano-CaO-based CO<sub>2</sub> sorbent in calcium looping. *Fuel* 143: 9-15.
16. Wu SF, Zhu YQ (2010) Behavior of CaTiO<sub>3</sub>/Nano-CaO as a CO<sub>2</sub> reactive adsorbent. *Ind Eng Chem Res* 49(6): 2701-2706.

For possible submissions Click below:

[Submit Article](#)